

Reliable Electronic and Magnetic Structure for BaFe_2As_2 using the PAW method

Chao Cao,* Yu-ning Wu, Rashid Hamdan, and Hai-Ping Cheng†

*Department of Physics and Quantum Theory Project,
University of Florida, Gainesville, FL 32611, U.S.A.*

(Dated: May 12, 2009)

By carefully choosing parameters and including more semi-core orbitals as valence electrons, we constructed a high quality projected augmented wave (PAW) dataset that yields results comparable to existing full-potential linearized augmented plane-wave calculations. The dataset was then applied to BaFe_2As_2 to study the effect of different levels of structure optimization, as well as different choices of exchange-correlation functionals. It is found that the LDA exchange-correlation functional fails to find the correct SDW-AFM ground state under full optimization, while PBE obtains the correct state but significantly overestimates the magnetism. The electronic structure of the SDW-AFM state is not very sensitive to structure optimizations with the PBE exchange-correlation functional because the position of the As atoms are preserved under optimizations.

The recent discovery of iron pnictide superconductor parental materials LnFeAsO (1111)¹, AeFe_2As_2 (122)², and AFeAs (111)^{3,4} has stimulated tremendous interest and attention starting about a year ago. From the very beginning, various efforts have been made in order to determine the structure and electronic and magnetic properties of these materials from first principles^{5,6,7,8}. Both the local density approximation (LDA) and generalized gradient approximation (GGA) to the exchange-correlation functional have been employed, while for electron-iron interactions, various methods including ultrasoft pseudopotential^{6,8,9} (USPP), projected augmented wave¹⁰ (PAW), and full-potential linearized augmented plane-wave^{5,7,11} (FLAPW) were used. While FLAPW is generally regarded as the most accurate method among the three, it is computationally much more expensive than both USPP and PAW methods. Therefore, study using FLAPW often does not involve full relaxation including the unit cell parameters. For USPP and PAW, previous studies showed that both methods tend to overestimate the local magnetic moment on individual Fe atoms as well as the relative energy differences between different magnetic states^{6,7,8}, indicating a serious problem regarding the commonly-used current pseudopotential or PAW datasets. Although it is now widely perceived that the calculated electronic structure is only comparable with experiments when the crystal structure is fixed as experimentally measured, this statement has never been verified under full relaxation using FLAPW or reliable USPP/PAW calculations. It is also a question for this system if the LDA exchange-correlation functional is superior to GGA or vice versa. In this paper, we report our efforts to generate a reliable PAW dataset for these materials, exemplified by BaFe_2As_2 . We compare all of our results with FLAPW results in detail whenever feasible, and we study the influence due to full relaxation of the crystal structure as well as different exchange-correlation functionals on the calculated results.

In principle, one can approach all-electron accuracy with pseudopotential or PAW methods by including more semi-core orbitals into valence orbitals, but in practice it

atom	PAW		USPP	
	valence	r_{cut}	valence	r_{cut}
Fe	3s 3p 3d 4s 4p	2.0 (2.1 ^d)	3d 4s 4p	2.2 (2.3 ^d)
Ba	5s 5p 5d	2.9	5s 5p 6s	2.5 (2.1 ^p)
As	4s 4p 3d	2.1	4s 4p	2.4 (2.1 ^p)

TABLE I: parameters used to generate the PAW datasets in this paper. r_{cut} unit is in bohr, the number in the bracket indicates the value used for the orbitals with angular momentum represented by the superscript.

is prohibitively difficult to do so for the ultrasoft pseudopotential method. Nevertheless, this process is practical with Blöch's PAW method¹⁰. For this study, we follow the slightly modified recipe by Kresse *et al.*¹², as implemented in the PWSCF package¹³. The valence orbitals (including the semi-core orbitals) included in the datasets are listed in TABLE I, compared with previous pseudopotentials. The generated dataset was carefully tested with logarithmic derivatives, ionization potentials, and simple crystal structures. The logarithmic derivative energy range considered was taken to be from -7.0 Ry to 3.0 Ry, and orbital angular momentum l from 0 to 4 (s , p , d , f , g). These tests ensured the quality of the PAW dataset. Throughout this paper, we used a cutoff energy of 40 Ry for plane-waves in both PAW and USPP calculations to ensure convergence, and the irreducible Brillouin zones were sampled with the Monkhorst-Pack scheme¹⁴, $8 \times 8 \times 8$ for the body-centered tetragonal (bct) unit cell (non-magnetic NM/checker-board antiferromagnetic CB-AFM states), $6 \times 6 \times 8$ for the base-centered orthorhombic (bco) unit cell (spin-density wave antiferromagnetic SDW-AFM state). Both LDA and Perdew-Burke-Ernzerhof (PBE) parameterizations¹⁵ to GGA were used.

In order to directly compare with existing literatures using FLAPW method, we calculated the BaFe_2As_2 parental compound with different structural parameters. These calculations were performed on the structures used in Ref. 16, using NM lattice parameters with relaxed z_{As} and with experimental z_{As} . It should be noted that both

	SDW-AFM		CB-AFM	
	<i>unrelaxed</i>	<i>opt-z_{As}</i>	<i>unrelaxed</i>	<i>opt-z_{As}</i>
$m_{\text{Fe}} (\mu_B)$				
FLAPW	1.75	0.70	1.60	N/A
PAW	1.75(2.34)	0.60(1.60)	1.54	N/A
USPP	2.12	1.04	1.90	0.58
ΔE (meV)				
FLAPW	92	N/R	41	N/A
PAW	65(174)	< 1(28)	19	N/A
USPP	119	6.9	60	< 1

TABLE II: Comparison between our PAW-LDA results with FLAPW¹⁶ and USPP results with the same structure used in Ref. 16. z_{As} refers to optimized z_{As} with experimental lattice constants, and *full-opt* means fully optimized structure with relaxed lattice constants. ΔE is the total energy relative to the NM state per iron atom. The PBE results are given in parentheses.

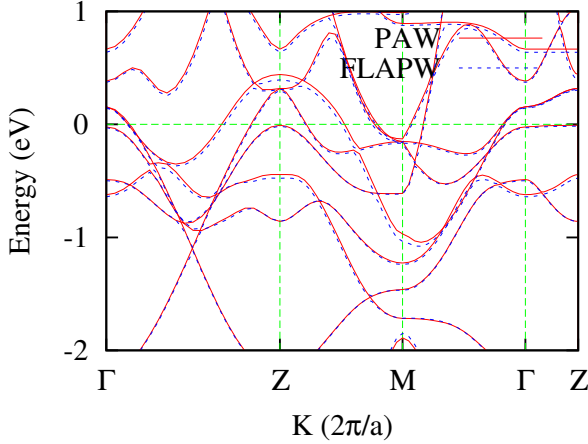


FIG. 1: Comparison between FLAPW band structure and our PAW result for the non-magnetic state Ba122 with relaxed z_{As} but fixed experimental lattice parameters (LDA result). The PAW result (red solid line) is almost exactly the same as the FLAPW result (blue dashed line).

these parameters were used for the SDW-AFM state as well. Results are listed in Table II. Our PAW calculations agree with FLAPW results very well including the local magnetic moment on Fe atoms, whereas USPP always exaggerate the magnetic moment, as reported previously. Using the LDA version of these datasets, we also calculated the band structure for the NM configuration relaxed- z_{As} structure. We compare our result and the FLAPW result in Fig. 1, and it is apparent from this plot that our datasets almost exactly reproduced the FLAPW band structure. From Table II, it is also observed that using the correct experimental lattice parameters for SDW-AFM configuration will remove some stress-induced magnetization on Fe atoms, and a further relaxation of z_{As} will eventually bring the local magnetic moment down to $0.4\mu_B/\text{Fe}$. In this situation, the SDW-AFM state energy is lower than the NM state energy by

	NM		SDW-AFM	
	<i>opt-z_{As}</i>	<i>full-opt</i>	<i>opt-z_{As}</i>	<i>full-opt</i>
a	3.963	3.873(3.968)	5.615	(5.697)
b	3.963	3.873(3.968)	5.574	(5.594)
c	13.02	12.14(12.49)	12.94	(12.76)
z_{As}	0.341(0.344)	0.347(0.346)	0.341(0.352)	(0.3514)
$m_{\text{Fe}} (\mu_B)$	0.0	0.0	1.62(2.14)	(2.19)
ΔE (meV)	0.0	0.0	105 (83)	(68)

TABLE III: Physical properties after different levels of structural optimization using PAW. The SDW-AFM state does not exist after full relaxation using LDA, thus only PBE results are provided. The values in parentheses are obtained with PBE.

22 meV/Fe. Neither FLAPW nor PAW is able to obtain a CB-AFM configuration with the relaxed z_{As} , but this configuration remains stable using USPP.

Next we evaluate different exchange-correlation functionals and study the band structure dependency on the degree structural optimization. As summarized in Table III, the PBE exchange-correlation functional always exaggerates the local magnetic moments on Fe atoms, and the magnetic moment remains relatively unchanged with respect to the structural optimizations. However, it should be noted that the PBE exchange-correlation functional yields crystal structures much closer to experiment, and the z_{As} parameters are significantly different using PBE and using LDA. PBE also yields a large magnetic moment change upon z_{As} optimization when the LDA crystal structure is used; see Table II data in parentheses. It was also observed that a full optimization of both lattice parameters and z_{As} within LDA fails to yield a SDW-AFM ground state (in fact, it does not show any magnetic instability after full optimization) due to the fact that LDA underestimates bond lengths/lattice constants while this system is too delicate to allow such underestimation. PBE overestimates both parameters, obtaining the correct ground state of the system under full optimization due to an error cancellation. Nevertheless, both exchange-correlation functionals underestimate the c -axis in both the NM and SDW-AFM states, indicating an incompleteness of LDA and GGA exchange-correlation functionals. Since the local magnetic moment of Fe atoms depends strongly on z_{As} parameters, as shown in previous studies and in this work, we conclude that for the magnetic properties, neither LDA nor PBE is capable of describing the subtleness of this particular system; but PBE correctly describes the ground state of the system under full optimization.

Due to the loss of the SDW-AFM ground state in LDA after full optimization, the following discussion includes PBE results only. As pointed out by Ref. 17 and 18, DFT calculations can be comparable with experimental results only if z_{As} is fixed at the experimental value. Thus, these calculations were performed with FLAPW without full optimization of lattice parameters. Figure 2 depicts a

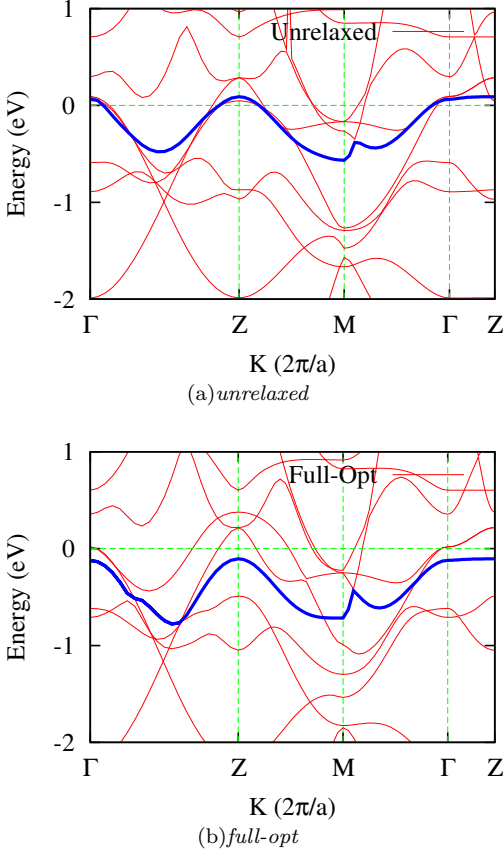


FIG. 2: Band structure for NM state Ba122 with (a) experimental structure, and (b) fully optimized lattice parameters as well as z_{As} using PBE exchange-correlation functional. The band structure for the *opt*- z_{As} structure looks very close to the LDA result (Fig. 1), and is therefore not shown here. The effect of structural optimization mostly appears in the thicker blue band.

set of band structures corresponding to different levels of structural optimization. Apparently, optimization does not alter significantly the electronic structure around the M point, where two electron pockets were found. Moreover, even the size of these electron pockets does not strongly depend on the structural optimization. In contrast, the structural relaxation substantially changed the band structure around Γ and Z. The main effect of structural relaxation is optimization pushes one of the Fe 3d-bands toward lower energy (the thicker blue solid line in Fig. 2); thus, only the two hole pockets from the rest of the 3d-bands remains after z_{As} optimization as well as after full structural relaxation.

Unlike the NM state, the band structure of SDW-AFM state does not exhibit large variation before and after structural optimization (Fig. 3). This can be easily understood since z_{As} in SDW-AFM state was maintained during structure relaxation. We have used the SDW-AFM experimental structure and calculated the band structure with LDA, and there is not much difference

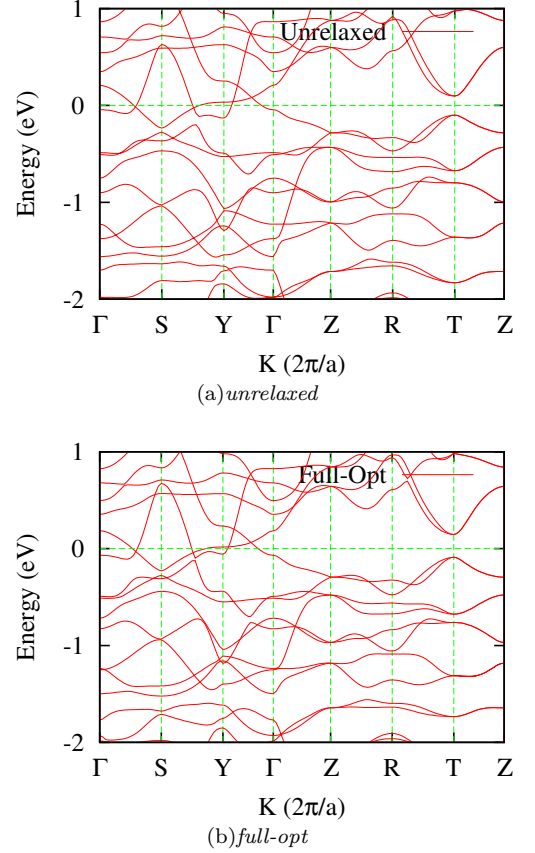


FIG. 3: Band structure for SDW-AFM state Ba122 with (a) experimental structure, and (b) fully optimized lattice parameters as well as z_{As} using PBE exchange-correlation functional. Due to the spin degeneracy, only the α spin band structure is shown here.

between the LDA result and the ones shown in Fig 3, despite of the significant difference ($0.5 \mu_B$) in the m_{Fe} found in these calculations. It is then apparent that the fundamental discrepancy between the LDA and the GGA calculations in the previous literature is due to the difference between the structure optimized with LDA and GGA, respectively. The full optimization with the PBE exchange-correlation functional does not significantly alter the band structure in the SDW-AFM state, but is crucial to study realistic doping and pressure effects in order to be consistent.

Finally, we present the Fermi surfaces reconstructed using maximally localized Wannier functions^{19,20} (ML-WFs) (Fig. 4). For the NM state, as we have seen in Fig. 2, the optimization leads to very different band structures, thus results in very different Fermi surfaces as well. After full-optimization, the size of hole pockets around Γ is greatly reduced and the two electron pockets are much less affected, as suggested by the band structure calculation, and therefore the expected (π, π) Fermi-surface nesting is missing. For the SDW state, since the optimization does not significantly alter the electronic structure as it

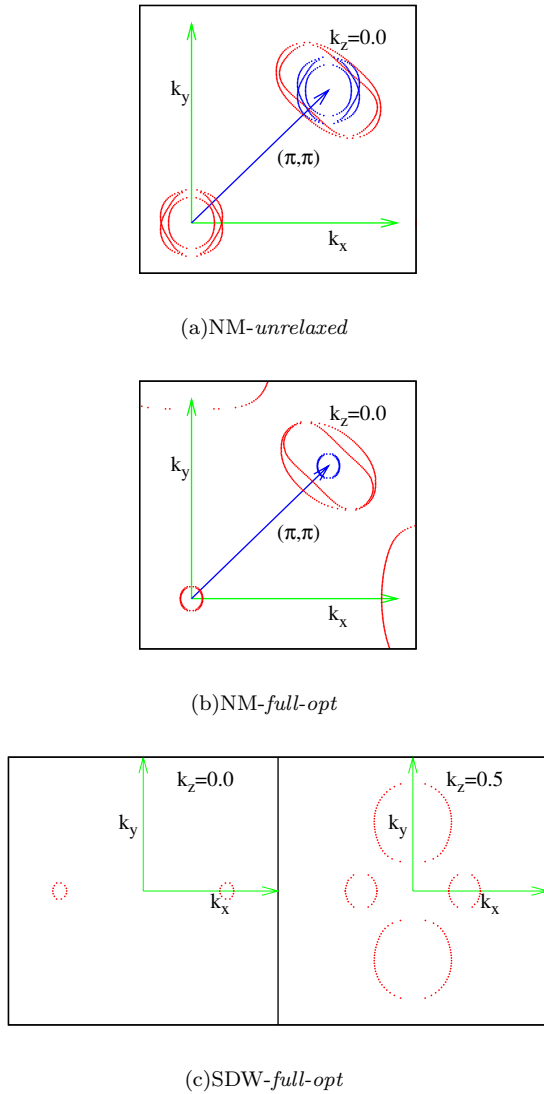


FIG. 4: Fermi surfaces reconstructed using maximally localized Wannier functions (MLWFs). k_x and k_y denote the reciprocal vectors corresponding to a and b for the conventional tetragonal unit cell.

does in the NM state, we thus show only the Fermi surfaces after full optimization. Unlike its NM state, the SDW Fermi surfaces are surprisingly simple and do not show very interesting features such as Fermi-surface nesting. Two extended electron pockets were found, and two hole pockets appear around $k_z = 0.5$.

In conclusion, we have constructed a reliable PAW dataset that yields results comparable to the FLAPW method, that is then used to study electronic and magnetic structure for BaFe_2As_2 . A thorough comparison between exchange-correlation functionals as well as structural optimizations were presented. It is found that the LDA exchange-correlation functional will miss the SDW-AFM configuration under full structural optimization, and the PBE gives the correct ground state. The important c -axis lattice parameter and z_{As} can be obtained within reasonable error for the SDW-AFM state with the PBE exchange-correlation functional, but both values are noticeably reduced for the NM state. Therefore, the electronic structure of the SDW-AFM state is insensitive to structural optimization, but the optimization will yield unacceptable electronic structure for the NM state. PBE can describe the SDW-AFM ground state very well but not the NM state, and the LDA fails for both. Based on the apparent correlation between magnetism and crystal structure, we therefore propose that LDA/GGA fails for the NM state because of a strong magnetic-phonon coupling within the iron-pnictide compounds, and that this strong coupling may be the mechanism for the electron pairing. We suggest future study to focus on the magnetic-phonon coupling effect.

This work is supported by NSF-DMR. The authors would like to thank the UF-HPC center, ORNL CNMS user program, and DOE/NERSC for the computational resources that have contributed to the research results reported within this paper.

* Electronic address: cao@qtp.ufl.edu

† Electronic address: cheng@qtp.ufl.edu

¹ Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).

² M. Rotter, M. Tegel, and D. Johrendt, *Phys. Rev. B* **78**, 020503 (2008).

³ M. J. Pitcher, D. R. Parker, P. Adamson, S. J. C. Herkelrath, A. T. Boothroyd, R. M. Ibberson, M. Brunelli, and S. J. Clarke, *Chem. Commun.* p. 5918 (2008).

⁴ J. H. Tapp, Z. Tang, B. Lv, K. Sasmal, B. Lorenz, P. C. W. Chu, and A. M. Guloy, *Phys. Rev. B* **78**, 060505(R) (2008).

⁵ D. J. Singh and M.-H. Du, *Phys. Rev. Lett.* **100**, 237003 (2008).

⁶ C. Cao, P. J. Hirschfeld, and H.-P. Cheng, *Phys. Rev. B* **77**, 220506 (2008).

⁷ T. Yildirim, *Phys. Rev. Lett.* **101**, 057010 (2008).

⁸ T. Yildirim, *Phys. Rev. Lett.* **102**, 037003 (2009).

⁹ D. Vanderbilt, *Phys. Rev. B* **41**, 7892 (1990).

¹⁰ P. E. Bloch, *Phys. Rev. B* **50**, 17953 (1994).

¹¹ D. Singh and L. Nordstrom, *Planewaves, Pseudopotentials and the LAPW Method, 2nd. Ed.* (Springer, Berlin, 2006).

¹² G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).

¹³ *PWSCF in Quantum Espresso Package* (2007), URL <http://www.pwscf.org>.

¹⁴ H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).

¹⁵ J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev.*

- Lett. **77**, 3865 (1996).
- ¹⁶ D. J. Singh, Phys. Rev. B **78**, 094511 (2008).
 - ¹⁷ D. Kasinathan, A. Ormeci, K. Koch, U. Burkhardt, W. Schnelle, A. Leithe-Jasper, and H. Rosner, New J. Phys. **11**, 025023 (2009).
 - ¹⁸ S. A. J. Kimber, A. Kreyssig, Y. Zhang, H. Jeschke, R. Valentí, F. Yokaichiya, E. Colombier, J.-Q. Yan, T. C. Hansen, T. Chatterji, et al. (2009), in press, 10.1038/nmat2443.
 - ¹⁹ I. Souza, N. Marzari, and D. Vanderbilt, Phys. Rev. B **65**, 035109 (2001).
 - ²⁰ A. A. Mostofi, J. R. Yates, Y.-S. Lee, I. Souza, D. Vanderbilt, and N. Marzari, Comp. Phys. Comm. **178**, 685 (2008).

